

Mapping spin-orbit splitting in strained InGaAs epilayers

B. M. Norman,¹ C. J. Trowbridge,¹ J. Stephens,² A. C. Gossard,² D. D. Awschalom,² and V. Sih¹

¹*Department of Physics, University of Michigan, Ann Arbor, MI 48109*

²*Center for Spintronics and Quantum Computation,
University of California, Santa Barbara, CA 93106*

(Dated: June 30, 2010)

Time- and spatially-resolved Faraday rotation spectroscopy is used to measure the magnitude and direction of the momentum-dependent spin splitting in strained InGaAs epilayers. The epilayers are lattice-matched to the GaAs substrate and designed to reduce inhomogeneous effects related to strain relaxation. Measurements of momentum-dependent spin splitting as a function of electron spin drift velocity along [100], [010], [110] and $[1\bar{1}0]$ directions enable separation of isotropic and anisotropic effective magnetic fields that arise from uniaxial and biaxial strain along $\langle 110 \rangle$. We relate our findings to previous measurements and theoretical predictions of spin splitting for inversion symmetry breaking in bulk strained semiconductors.

PACS numbers: 71.70.Ej, 71.70.Fk, 72.25.Dc, 72.25.Rb

The polarization and coherent manipulation of electron spins are important steps towards the realization of spin-based information processing¹. While electron spins can be manipulated by magnetic fields, electrical control is desirable as it offers the potential for high-speed manipulation and local gates. Spin-orbit interactions in semiconductors offer momentum-dependent effective magnetic fields that can be used for electrical control^{2,3}.

Momentum \mathbf{k} -dependent spin splittings arise from the spin-orbit interaction and the breaking of spatial inversion symmetry. The lack of an inversion center in zincblende crystal structures results in a bulk inversion asymmetry (BIA) and the Dresselhaus field⁴. Structural inversion asymmetry (SIA) along the growth direction in heterostructures results in the Rashba field⁵. These internal effective magnetic fields have different \mathbf{k} -dependence and can be distinguished by changing the direction of the carrier drift momentum. Measurements as a function of electric field direction have mapped the \mathbf{k} -linear Rashba and Dresselhaus fields in quantum wells⁶.

Strain breaks spatial inversion symmetry, which results in additional \mathbf{k} -dependent spin splittings⁷⁻⁹. Strain-induced spin precession and characterization of \mathbf{k} -linear spin splitting have been conducted in lattice-mismatched heterostructures¹⁰ and using a mechanical vise¹¹⁻¹³. Measurements on lattice-mismatched heterostructures observed both BIA- and SIA-type splitting, but the splitting did not exhibit a clear trend as a function of measured strain¹⁰. A subsequent theoretical analysis proposed that variations in strain relaxation during growth could result in different \mathbf{k} -linear BIA-type splitting⁹. Measurements conducted using a mechanical vise found that uniaxial strain along $\langle 110 \rangle$ introduces a SIA-type splitting^{11,12}.

In this paper we investigate the momentum dependence of strain-induced spin-orbit splittings in $\text{In}_{0.04}\text{Ga}_{0.96}\text{As}$ epilayers. The InGaAs epilayers are grown on GaAs substrates, which introduces biaxial compressive strain, and the sample structure was designed to reduce inhomogeneous effects related to strain relax-

ation. Measurements of internal effective magnetic fields as a function of electron spin drift velocity along [100], [010], [110] and $[1\bar{1}0]$ enable separation of BIA and SIA-type spin splittings that arise from biaxial and uniaxial strain.

For \mathbf{k} in the plane perpendicular to the growth direction [001], the spin-splitting Hamiltonians take the form:

$$H_D = \lambda (\sigma_x k_x k_y^2 - \sigma_y k_y k_x^2) \quad (1)$$

$$H_R = \alpha (k_y \sigma_x - k_x \sigma_y) \quad (2)$$

$$H_1 = D (\epsilon_{zz} - \epsilon_{xx}) (\sigma_x k_x - \sigma_y k_y) \quad (3)$$

$$H_2 = \frac{C_3 \epsilon_{xy}}{2} (k_y \sigma_x - k_x \sigma_y) \quad (4)$$

H_D and H_R are the Dresselhaus and Rashba Hamiltonians, respectively, while H_1 and H_2 are two additional \mathbf{k} -linear terms due to strain⁷⁻⁹. Here x , y , and z denote the [100], [010], and [001] crystal axes, σ_i denotes the i^{th} Pauli matrix, ϵ_{ij} are the components of the strain tensor with $\epsilon_{xy} = \epsilon_{yx}$ and $\epsilon_{xx} = \epsilon_{yy}$, and λ , α , D , and C_3 are material constants. H_R and H_2 have the same direction dependence on momentum, while H_1 has the same form as the linear Dresselhaus field for a two-dimensional system with quantum confinement along [001]¹⁴. H_2 accounts for the spin splitting introduced by uniaxial strain along $\langle 110 \rangle$ ^{11,12,15}, and H_1 has been proposed⁹ to explain the BIA-type splitting in Ref. [10], despite earlier work⁷ that argued that H_1 should be small. The directions of the SIA-type (H_R and H_2) and BIA-type (H_D and H_1) fields are shown in Fig. 1(b). For \mathbf{k} along [110] and $[1\bar{1}0]$, the SIA and BIA fields are both perpendicular to \mathbf{k} and parallel to each other, while for \mathbf{k} along [100] and [010], the BIA fields are parallel to \mathbf{k} while the SIA fields are perpendicular to \mathbf{k} .

In general, H_D is cubic in \mathbf{k} while H_R , H_1 , and H_2 are linear in \mathbf{k} . Thus the spin splitting can be described by combinations of \mathbf{k} -linear and \mathbf{k} -cubic terms of the form

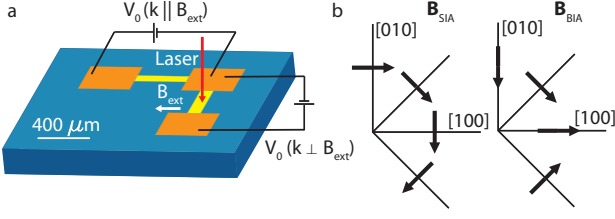


FIG. 1. (Color) (a) Experimental setup. InGaAs channels and contacts are shown in yellow and orange respectively. Voltage is applied such that the net electron drift momentum is either perpendicular to or parallel to the external magnetic field \mathbf{B}_{ext} . The red arrow denotes the laser propagation direction. (b) Directions of momentum-dependent effective internal fields due to spin-orbit interactions from structural inversion asymmetry (left) and bulk inversion asymmetry (right).

$\Delta = \alpha v_d^3 + \beta v_d$, where v_d is the in-plane drift velocity defined by $\hbar \mathbf{k}_d = m^* v_d$ with m^* the conduction band electron effective mass and $\hbar \mathbf{k}_d$ the drift momentum. Yet along the [010] axis, $k_x = 0$ and $k_y = |\mathbf{k}_d|$, so $H_D = 0$ for bulk systems. Similarly, $H_D = 0$ for \mathbf{k} along [100]. On the other hand, for momentum along [110], $k_x = k_y = \frac{k_d}{\sqrt{2}}$, and H_D reduces to $H_D = \frac{\lambda k_d^3}{2\sqrt{2}} (\sigma_x - \sigma_y)$.

The momentum-dependent effective magnetic fields described above were measured using pump-probe optical techniques. Optical orientation of electron spins results in an out-of-plane spin polarization, which can precess about in-plane internal and applied external magnetic fields. Measurements were performed on Si-doped $\text{In}_{0.04}\text{Ga}_{0.96}\text{As}$ epilayers (doping concentration $n = 3 \times 10^{16} \text{ cm}^{-3}$). The thickness of the InGaAs layer is 500 nm, grown above a 300 nm growth interrupted GaAs buffer layer on a (001) GaAs substrate and capped with 100 nm undoped GaAs. X-ray diffraction measurements show that the InGaAs epilayer is lattice-matched to the GaAs substrate and exhibits minimal strain relaxation. Samples were fabricated, consisting of two perpendicular InGaAs channels [Fig. 1(a)]. Channels were aligned along [110], $[1\bar{1}0]$, [100] and [010]. The channels were each 400 μm long and 100 μm wide with 400 x 400 μm^2 ohmic contacts at each end. Wires were soldered to each of the contacts and connected to an external voltage source. The samples were mounted in a liquid helium flow cryostat with measurements made at temperature $T = 30$ K. Care was taken during sample mounting to minimize introducing additional strain.

Measurements were conducted using a mode-locked Ti:Sapphire laser with a repetition rate of 76 MHz tuned to the band edge of the InGaAs epilayer ($\lambda = 848$ nm). The laser was separated into a pump and probe pulse with a temporal separation controlled by a mechanical delay line. The pump and probe beams were modulated by a photoelastic modulator (PEM) and optical chopper respectively for cascaded lock-in detection. An external magnetic field was applied in the plane of the layer and varied from -40 to 40 mT. The inclusion of a motor

driven steering mirror in the pump path allowed control of the pump-probe spatial separation on the sample. Field scans were taken at 5 μm intervals over a 40 μm range (roughly ± 20 μm from the center of the electron spin packet). By applying an external voltage to the contacts, the electron drift momentum was varied along each channel. Measurements were performed with the channels oriented both parallel with and perpendicular to the applied magnetic field to measure both the magnitude and direction of the internal magnetic fields.

Faraday rotation (FR) of the probe pulse can be described by:

$$\theta_F = A e^{-\frac{\Delta t}{T_2^*}} \cos \left(\frac{g \mu_B \Delta t}{\hbar} |\mathbf{B}_{\text{ext}} + \mathbf{B}_{\text{int}}| \right) \quad (5)$$

where A is the FR amplitude, g is the electron g factor, μ_B is the Bohr magneton, T_2^* is the inhomogeneous dephasing time, Δt is the pump-probe time delay, and \mathbf{B}_{ext} is the applied external magnetic field. Time-resolved FR measurements¹⁶ find that $g = 0.51$ and $T_2^* = 7.8$ ns. The direction and magnitude of the internal magnetic field \mathbf{B}_{int} , which is proportional to the spin splitting $\Delta = g \mu_B |\mathbf{B}_{\text{int}}|$, is determined from fits of the FR signal to Eq. 5 with errors less than 1%. As shown in Fig. 2(a), the component of \mathbf{B}_{int} that is parallel to \mathbf{B}_{ext} causes an overall shift in the field-dependent signal, and the component that is perpendicular to \mathbf{B}_{ext} changes the magnitude of the center peak. B_{\parallel} (B_{\perp}) is defined as the component of \mathbf{B}_{int} that is parallel (perpendicular) to \mathbf{k}_d , as determined from field scans based on the channel orientation. Measurements were taken with $\mathbf{k} \perp \mathbf{B}_{\text{ext}}$ and $\mathbf{k} \parallel \mathbf{B}_{\text{ext}}$ to determine both the sign and magnitude of the spin splitting. The magnitude of the drift momentum was varied by changing the potential applied to the channels, in the range between -2.0V and 2.0V. Scans with varying pump-probe spatial separations were taken to characterize the internal field and drift velocity of the optically injected spin packet [Fig. 2]. The drift velocity v_d of the spin packet at each voltage is the measured spatial drift of the spin packet center x_c during the pump-probe time delay $\Delta t = 13$ ns.

For the [010] channel oriented perpendicular to the external magnetic field, values of B_{\perp} and B_{\parallel} are displayed for various contact voltages as a function of pump-probe spatial separation in Fig. 3. The amplitude of the FR is also fit for each scan to determine the position of the spin packet center x_c at each voltage [Fig. 3(c)]. The spatial dependence of \mathbf{B}_{int} is due to both drift and diffusion of the spin packet¹⁰. For the [010] channel, it is expected that \mathbf{B}_{int} has a linear dependence on \mathbf{k} because $H_D = 0$. For each voltage, a linear fit is used to determine the value of \mathbf{B}_{int} at x_c . These values are fit to linear functions of v_d [Fig. 3(d)] to determine the values of β_{\perp} and β_{\parallel} .

Table 1 shows a summary of the measured values of β_{\perp} and β_{\parallel} for all four channel directions and both measurement orientations, $\mathbf{k} \parallel \mathbf{B}_{\text{ext}}$ and $\mathbf{k} \perp \mathbf{B}_{\text{ext}}$. All of the measurements are well described by a linear dependence

	$k \parallel B_{ext}$				$k \perp B_{ext}$			
Channel	β_{\parallel}	β_{\perp}	$C_3\epsilon_{xy}/\hbar$	$D(\epsilon_{zz} - \epsilon_{xx})/\hbar$	β_{\parallel}	β_{\perp}	$C_3\epsilon_{xy}/\hbar$	$D(\epsilon_{zz} - \epsilon_{xx})/\hbar$
[100]	35	-84	-230	47	35	-110	-300	47
[010]	-35	-100	-280	48	-41	-91	-250	56
[110]	0	-14	-180	70	0	-20	-150	50
[1 $\bar{1}$ 0]	0	-120	—	—	0	-94	—	—

TABLE I. Measured β_{\parallel} and β_{\perp} for each channel and orientation expressed in units of $\text{neV ns } \mu\text{m}^{-1}$. β_{\parallel} represents the BIA spin splitting, while β_{\perp} represents either the SIA ([100] and [010] channels), SIA plus BIA ([110]) or SIA minus BIA ([1 $\bar{1}$ 0]) spin splitting. Calculated strain parameters $C_3\epsilon_{xy}/\hbar$ and $D(\epsilon_{zz} - \epsilon_{xx})/\hbar$ are in units of m/s .

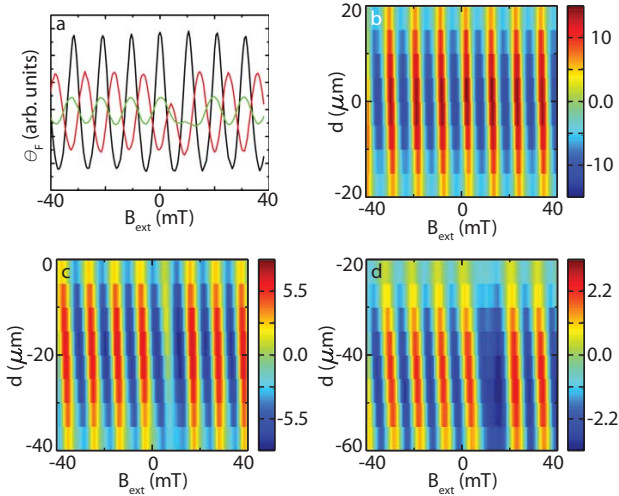


FIG. 2. (Color) (a) Faraday rotation θ_F as a function of external magnetic field \mathbf{B}_{ext} for 0.0V (black), 1.0V (red) and 2.0V (green) measured at the center of the spin packet. The [010] channel was oriented perpendicular to \mathbf{B}_{ext} , so the shift and decrease in the center peak give the values of B_{\perp} and B_{\parallel} respectively. (b)-(d) Faraday rotation as a function of \mathbf{B}_{ext} and pump-probe separation d for (b) 0.0V, (c) 1.0V, and (d) 2.0V. The data was measured at $T = 30$ K with a pump-probe time delay of $\Delta t = 13$ ns.

of \mathbf{B}_{int} with \mathbf{k} , so $\beta = \Delta/v_d$. Measurements with $\mathbf{k} \parallel \mathbf{B}_{ext}$ and $\mathbf{k} \perp \mathbf{B}_{ext}$ show reasonable agreement, but with noticeable discrepancies that are larger than the measurement error, which is typically on the order of 1 – 5 %. Additional strain introduced during sample mounting and cool-down could possibly account for these discrepancies. For the [100] and [010] channels for which the SIA- and BIA-type spin splittings can be separated, we found that the SIA splitting (β_{\perp}) is consistently 2 or 3 times larger than the BIA splitting (β_{\parallel}). For the [010] channel, the value of β_{\perp} can be attributed to H_R and H_2 and β_{\parallel} to H_1 , since $H_D = 0$ for \mathbf{k} along [010]. Also, as expected from the form of H_1 [Eq. 3], the BIA-type splitting (β_{\parallel}) has similar magnitude but opposite sign for [100] and [010], which justifies the assumption that ϵ_{xx}

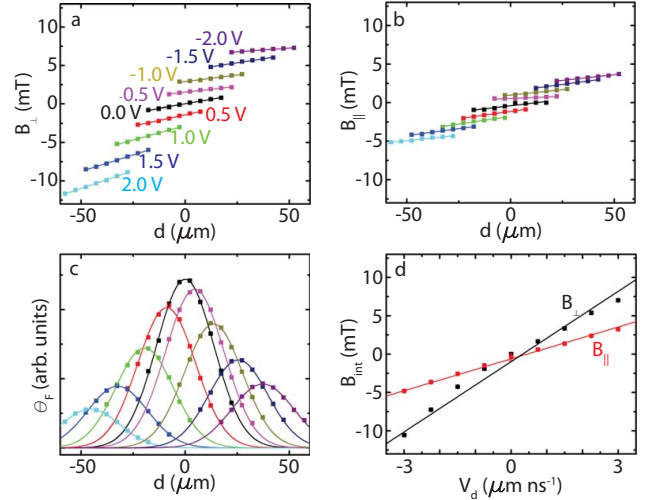


FIG. 3. (Color) Internal magnetic fields (a) perpendicular to and (b) parallel to the channel direction for the [010] channel at $T = 30$ K with a pump-probe time delay of $\Delta t = 13$ ns. For these measurements, the channel was oriented perpendicular to the applied magnetic field ($\mathbf{k} \perp \mathbf{B}_{ext}$). Applied voltages are the same for (a)-(c). Lines in (a) and (b) are linear fits. (c) Faraday rotation amplitude as a function of pump-probe separation for various potential differences used to determine the spin packet center x_c . (d) B_{\perp} (black) and B_{\parallel} (red) evaluated at x_c as a function of spin packet drift velocity. The slope of the linear fit gives the value of $\beta/g\mu_B$. Errors in (a)-(c) are smaller than the data points.

$= \epsilon_{yy}$ for this sample.

Although the measurements cannot distinguish between the contributions of H_R and H_2 , previous measurements indicate that the effect of H_2 is greater than that of H_R for similar bulk epilayers. Measurements¹⁰ on unstrained n-doped GaAs epilayers found $\beta < 10 \text{ neV ns } \mu\text{m}^{-1}$, and that the measured spin splitting upon applied strain could be characterized using H_2 and without requiring H_R ^{11–13}.

From Eqs. 3 and 4 and the measured values of β , we calculate the sample parameters $C_3\epsilon_{xy}/\hbar$ and $D(\epsilon_{zz} - \epsilon_{xx})/\hbar$ assuming no contribution from H_D and H_R and $m^* = 0.065m_0$ ¹⁷, where m_0 is the free electron mass.

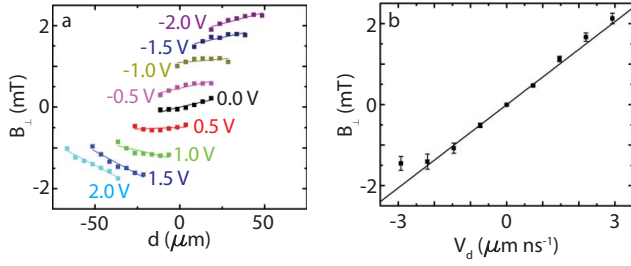


FIG. 4. (Color) (a) Internal magnetic field perpendicular to \mathbf{k} measured with $\mathbf{k} \perp \mathbf{B}_{\text{ext}}$ for the [110] channel at $T = 30$ K as a function of pump-probe separation d and with a pump-probe time delay of $\Delta t = 13$ ns. (b) Internal magnetic field evaluated at the spin packet center as a function of electron spin packet velocity. The slope of the linear fit gives the value of $\beta/g\mu_B$. Errors in (a) are smaller than the data points.

From the measurements on the [100] and [010] channels, $C_3\epsilon_{xy}/\hbar$ has an average value of -270 m/s, and $D(\epsilon_{zz} - \epsilon_{xx})/\hbar = 50$ m/s. From Ref. [9], $C_3/\hbar = 8 \times 10^5$ m/s and $D/\hbar = (0.5 - 1.5) \times 10^4$ m/s. From the literature value of C_3/\hbar and the range of values of $C_3\epsilon_{xy}/\hbar$ measured here, $\epsilon_{xy} = -0.029 - -0.038\%$. Therefore, the variation in our measurements indicates that the strain changes by an amount less than $|\Delta\epsilon_{xy}| = 1 \times 10^{-4}$ between different sample mountings and cool-downs. For pseudomorphic $\text{In}_{0.04}\text{Ga}_{0.96}\text{As}$ on GaAs ¹⁸, $\epsilon_{xx} = -0.29\%$ and $\epsilon_{zz} = 0.26\%$, which yields $D/\hbar = 0.9 \times 10^4$ m/s, which is in the same range as previously reported values^{9,10}. The data and analysis show that the measured spin splittings are consistent with H_1 and H_2 and that H_2 can have comparable magnitude to H_1 , which contradicts the argument that H_1 is small and can be neglected^{7,15}.

Unexpectedly, the values of β_{\perp} for the $[1\bar{1}0]$ and $[110]$ channels do not match the difference and sum, respectively, of the SIA and BIA terms from the other channels. Therefore, measurements along $[110]$ and $[1\bar{1}0]$ may not be sufficient to accurately characterize H_1 and H_2 . For $[110]$, $\beta_{\perp} = -14$ neV ns μm^{-1} for $\mathbf{k} \parallel \mathbf{B}_{\text{ext}}$ and -20 neV ns μm^{-1} for $\mathbf{k} \perp \mathbf{B}_{\text{ext}}$. These values are both smaller in magnitude than the average sum $(\beta_{\perp} + |\beta_{\parallel}|) = -58$ neV ns μm^{-1} from measurements on the $[100]$ and

$[010]$ channels. Similarly, for $[1\bar{1}0]$, $\beta_{\perp} = -120$ neV ns μm^{-1} for $\mathbf{k} \parallel \mathbf{B}_{\text{ext}}$ and -94 neV ns μm^{-1} for $\mathbf{k} \perp \mathbf{B}_{\text{ext}}$, and both values are smaller in magnitude than the average difference $(\beta_{\perp} - |\beta_{\parallel}|) = -130$ neV ns μm^{-1} . We also calculate $C_3\epsilon_{xy}/\hbar$ and $D(\epsilon_{zz} - \epsilon_{xx})/\hbar$ assuming that $H_1 \propto (\beta_{[110]} - \beta_{[1\bar{1}0]})/2$ and $H_2 \propto (\beta_{[110]} + \beta_{[1\bar{1}0]})/2$ and obtain a smaller value for $C_3\epsilon_{xy}/\hbar$. The calculated $C_3\epsilon_{xy}/\hbar$ and $D(\epsilon_{zz} - \epsilon_{xx})/\hbar$ values are included in Table 1. We hypothesize that higher order terms, including the additional \mathbf{k} -cubic Dresselhaus term (H_D) for $[110]$ and $[1\bar{1}0]$, could account for this discrepancy.

We also observe unexpected behavior in the measured slope of \mathbf{B}_{int} as a function of pump-probe spatial separation and voltage for the $[110]$ channel. The slope of \mathbf{B}_{int} at each voltage is due to diffusion and the distribution of drift velocity of the spin packet from the finite spot size ($30 \times 10 \mu\text{m}$) of the pump and probe beams¹⁰. Electrons at the leading edge of the packet have a higher average velocity than those in the back and thus we expect a non-zero and positive slope. However, as shown in Fig. 4(a), for scans in the voltage range $1.0 - 2.0$ V for the $[110]$ sample, surprisingly, a negative slope is observed. This was found from repeated measurements on different spots along the channel and is therefore not thought to be a result of any interface reflection effects. The measurements of β do not seem to be affected, as the value for \mathbf{B}_{int} for the center of the spin packet at each voltage still has a linear dependence on spin drift velocity, as shown in Fig. 4(b). Measurements for both configurations $\mathbf{k} \parallel \mathbf{B}_{\text{ext}}$ and $\mathbf{k} \perp \mathbf{B}_{\text{ext}}$ show reasonable agreement, with values for β_{\perp} of -14 and -20 neV ns μm^{-1} , respectively. The smaller spin splitting could possibly explain why this behavior is only apparent in the $[110]$ sample. Larger values of β could overwhelm this effect in other channels.

This material is based upon work supported by the National Science Foundation under Grants No. ECCS-0844908 and DMR-0801388 and the Horace H. Rackham School of Graduate Studies. Sample fabrication was performed in the Lurie Nanofabrication Facility, part of the NSF funded NNIN network.

- ¹ S. A. Wolf, D. D. Awschalom, R. A. Buhrman, J. M. Daughton, S. von Molnar, M. L. Roukes, A. Y. Chtchelkanova, and D. M. Treger, *Science* **294**, 1488 (2001).
- ² S. Datta and B. Das, *Appl. Phys. Lett.* **56**, 665 (1990).
- ³ D. Awschalom and N. Samarth, *Physics* **2**, 50 (2009).
- ⁴ G. Dresselhaus, *Phys. Rev.* **100**, 580 (1955).
- ⁵ Y. A. Bychkov and E. I. Rashba, *J. Phys. C* **17**, 6039 (1984).
- ⁶ L. Meier, G. Salis, I. Shorubalko, E. Gini, S. Schon, and K. Ensslin, *Nature Physics* **3**, 650 (2007).
- ⁷ G. E. Pikus and A. N. Titkov, in *Optical Orientation*, edited by F. Meier and B. P. Zakharchenya (Elsevier Science Publishers, Amsterdam, 1984).

- ⁸ G. C. La Rocca, N. Kim, and S. Rodriguez, *Phys. Rev. B* **38**, 7595 (1988).
- ⁹ B. A. Bernevig and S.-C. Zhang, *Phys. Rev. B* **72**, 115204 (2005).
- ¹⁰ Y. Kato, R. C. Myers, A. C. Gossard and D. D. Awschalom, *Nature* **427**, 50 (2004).
- ¹¹ S. A. Crooker and D. L. Smith, *Phys. Rev. Lett.* **94**, 236601 (2005).
- ¹² M. Beck, C. Metzner, S. Malzer and G. H. Dohler, *Europhys. Lett.* **75**, 597 (2006).
- ¹³ V. Sih, H. Knotz, J. Stephens, V. R. Horowitz, A. C. Gos-

- sard, and D. D. Awschalom, Phys. Rev. B **73**, 241316(R) (2006).
- ¹⁴ R. Winkler, *Spin-Orbit Coupling Effects in Two-Dimensional Electron and Hole Systems*, Springer Tracks in Modern Physics Vol. 191 (Springer, Berlin, 2003).
- ¹⁵ M. Hruska, S. Kos, S. A. Crooker, A. Saxena and D. L. Smith, Phys. Rev. B **73**, 075306 (2006).
- ¹⁶ S. A. Crooker, D. D. Awschalom, J. J. Baumberg, F. Flack and N. Samarth, Phys. Rev. B **56**, 7574 (1997).
- ¹⁷ I. Vurgaftman, J. R. Meyer, and L. R. Ram-Mohan, J. Appl. Phys. **89**, 5815 (2001).
- ¹⁸ S. C. Jain, M. Willander, and H. Maes, Semicond. Sci. Technol. **11**, 641 (1996).